



# Effects of Polypropylene Fibres on the Properties of Reinforced Structural Lightweight Concrete Made With Expanded Clay Aggregates

K.K. Gaayathri<sup>1\*</sup>, K. Suguna<sup>1</sup>, P.N. Raghunath<sup>1</sup>

<sup>1</sup> Department of Civil and Structural Engineering, Annamalai University, INDIA.

\*Corresponding Author (Email: [gaayathrikk14@gmail.com](mailto:gaayathrikk14@gmail.com))

Paper ID: 13A5H

Volume 13 Issue 5

Received 14 January 2021

Received in revised form 8 April 2022

Accepted 15 April 2022

Available online 22 April 2022

## Keywords:

Compressive strength;  
Expanded Clay  
Aggregate (ECA);  
Flexural strength;  
Lightweight concrete;  
Modulus of elasticity;  
Modulus of rupture;  
Polypropylene fibres.

## Abstract

All efforts are being made to tailor the properties of concrete by replacing binder and filler with appropriate materials based on the environmental conditions. Many prospective players came into vogue for the purpose. Expanded clay showed promise for use in structural lightweight concrete. The addition of discontinuous discrete fibres proved to be beneficial in further improving the performance of structural lightweight concrete. A comprehensive laboratory investigation has been carried out to assess the influence of polypropylene fibres on the properties of expanded clay-based structural lightweight concrete. Expanded clay aggregates (ECA) have been used in varying percentages of 10%, 20%, 30%, 40% to replace coarse aggregates. Polypropylene fibres have been used in volume fractions of 0.1%, 0.2%, 0.3% and 0.4%. Based on trials, the optimum dosage of expanded clay aggregates for meeting the workability and strength requirements has been obtained. The laboratory results showed that the inclusion of polypropylene fibres improved the properties of structural lightweight concrete appreciably.

**Disciplinary:** Civil Engineering & Technology (Structural & Construction Materials).

©2022 INT TRANS J ENG MANAG SCI TECH.

## Cite This Article:

Gaayathri, K.K., Suguna, K., Raghunath, P.N. (2022). Effects of Polypropylene Fibres on the Properties of Reinforced Structural Lightweight Concrete Made With Expanded Clay Aggregates. *International Transaction Journal of Engineering, Management, & Applied Sciences & Technologies*, 13(5), 13A5H, 1-11. <http://TUENGR.COM/V13/13A5H.pdf> DOI: 10.14456/ITJEMAST.2022.92

## 1 Introduction

Structural lightweight concrete is finding its place in many applications such as buildings, bridges, floors and partitions. The inherent characteristics of structural lightweight concrete that make it preferable include lower density, higher specific strength, good thermal insulation and better durability. The density of concrete is of primary concern in the context of the self-weight of

structural members. In many structures, self-weight forms an appreciable proportion of the total load. Reduced density of structural lightweight concrete results in reduced self-weight of structural members which is quite important in seismic-resistant design. It is relatively understandable that the addition of micro-reinforcement enhances the overall performance in general. The improved mechanical properties of structural lightweight concrete as a result of the inclusion of micro reinforcement makes it fit for use in load-bearing structural members also.

The addition of steel fibre to high strength lightweight concrete is extremely effective in improving the strength and fracture toughness (Jianming Gao et al. 1997). The longitudinal tensile reinforcement ratio compatible with flexural ductility is somewhat lower for LWAC beams when compared to NWAC (Bernardo et al. 2016). The methods contained in the American code of practice (ACI 318-2005 and ACI 213-2003) for LWAC can predict the cracking and ultimate strength quite accurately (Lim et al., 2006). The optimal HPPFs content of 1.1% and SFs content of 2.0% improved the flexural toughness of plain concrete (Li et al. 2017). The addition of 1.5% polypropylene fibre increased the compressive and split tensile strength. (Sohaib et al., 2018). The use of industrial waste steel wires can be used as micro-reinforcement for improving the mechanical properties of lightweight concrete. (Aghaee et al., 2014).

In this study, efforts have been made to study the behaviour of expanded clay-based structural lightweight concrete with the inclusion of polypropylene fibres in varying volume fractions.

In building systems, the dead load is of greater concern. Attempts need to be made to reduce the dead load as much as practicable. In this context, structural lightweight concrete gains importance (Sakthivel and Saravanan, 2022; Thongjub et al., 2022). The introduction of fibres into lightweight concrete enhances its flexural strength, compressive strength and deformation capacity appreciably. The sizes of member sections also get reduced leading to an economical solution. Further the serviceability of member sections also improves through reduced crack widths. Hence an attempt has been made to realise the impact of including polypropylene fibres on the properties of expanded clay-based structural lightweight concrete.

## 2 Experimental Programme

### 2.1 Materials

#### 2.1.1 Cement

Ordinary Portland Cement of grade 53 conforming to IS 12269: 2013 was used in this investigation. The properties of cement used are given in Table 1.

**Table 1: Properties of Cement**

| Property             | Value       |
|----------------------|-------------|
| Specific gravity     | 3.15        |
| Standard consistency | 33%         |
| Initial setting time | 55 minutes  |
| Final setting time   | 380 minutes |

### 2.1.2 Coarse Aggregate

The coarse aggregate used was crushed granite of a maximum particle size of 20mm and conforming to IS 383:2016. Expanded Clay Aggregate (ECA)(Figure2) was used to partially replace coarse aggregate.

**Table 2: Properties of Coarse Aggregate**

| Property         | Crushed Granite Aggregate | Expanded Clay Aggregate |
|------------------|---------------------------|-------------------------|
| Specific gravity | 2.68                      | 0.57                    |
| Water absorption | 0.7                       | 15.5%                   |
| Shape            | Angular                   | Rounded                 |
| Bulk density     | 1600 kg/m <sup>3</sup>    | 600 kg/m <sup>3</sup>   |

### 2.1.3 Fine Aggregate

A combination of natural river sand (R-sand) conforming to IS383: 2016 and manufactured sand (M-sand) was used as fine aggregate in this study. Trials were made to arrive at the combination of R-sand to M-sand. R-sand 55% and M-sand 45% combined were found to be beneficial. The specific gravity of the combine was found to be 2.66.

### 2.1.4 Polypropylene Fibre

Commercially available Recron 3S fibres (Figure3) were used in this study. The fibres are compatible with all admixtures used in concrete which conform to ASTM C1116.

**Table 3: Properties of Polypropylene Fibres**


| Property           | Value      |
|--------------------|------------|
| Length             | 12mm       |
| Shape              | Triangular |
| Effective Diameter | 40 micron  |
| Specific Gravity   | 0.91       |
| Tensile Strength   | 4 GPa      |
| Elongation         | 90%        |
| Elasticity Modulus | 4000 MPa   |
| Alkaline Stability | Very good  |

### 2.1.5 Super Plasticizer

An SNF based high range water reducing admixture Conplast SP430 (Figure1) was used to satisfy the workability demand of each mix. The product Conplast SP430 conforms to ASTM C494. The dosage for all the mixes was arrived at through trials.

**Table 4: Properties of Super Plasticizer**

| Property         | Value  |
|------------------|--------|
| Appearance       | Liquid |
| Colour           | Brown  |
| Specific gravity | 1.18   |
| Chloride content | Nil    |

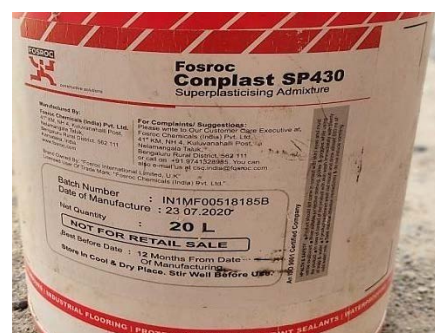

**Figure 1: Super Plasticizer**



**Figure 2: Expanded Clay Aggregates**



**Figure 3: Polypropylene Fibres**

## 2.2 Control Specimens

Cube Specimens (3 cubes for each mix) of size 150 X 150 X 150 mm were cast and tested for determining the compressive strength of concrete.

Cylinder Specimens (3 cylinders for each mix) of size 150 X 300 mm were cast and tested for determining the compressive strength of concrete.

Cylinder Specimens (3 cylinders for each mix) of size 150 X 300 mm were cast and tested for determining the elasticity modulus of concrete

Prism Specimens (3 prisms for each mix) of size 100 X 100 X 500 mm were cast and tested for determining the flexural strength of concrete.

### 2.2.1 Preparation of Control Specimens

The ingredients were first mixed in a dry state and then fibres were added in smaller quantities to avoid balling of fibres. The prepared wet (water plus SP) concrete was placed in equal layers in the moulds and thoroughly compacted. The specimens were removed after 24 hours from the moulds and then cured continuously for 28 days in a tank. After drying, the specimens were tested for compressive strength, elasticity modulus and flexural strength respectively. The details of control specimens are given in Table 5.

**Table 5: Details of Control Specimens**

| Mix No. | Specimen | w/c Ratio | Water content (kg) | Cement (kg) | Coarse Aggregate (kg) | Expanded Clay Aggregate (kg) | River Sand (kg) | M-Sand (kg) | Fibre Volume % |
|---------|----------|-----------|--------------------|-------------|-----------------------|------------------------------|-----------------|-------------|----------------|
| 1       | EC0      | 0.5       | 175                | 350         | 995.8                 | 52.17                        | 377.85          | 309.15      | 0              |
| 2       | EC1      | 0.5       | 175                | 350         | 995.8                 | 52.17                        | 377.85          | 309.15      | 0.1            |
| 3       | EC2      | 0.5       | 175                | 350         | 995.8                 | 52.17                        | 377.85          | 309.15      | 0.2            |
| 4       | EC3      | 0.5       | 175                | 350         | 995.8                 | 52.17                        | 377.85          | 309.15      | 0.3            |
| 5       | EC4      | 0.5       | 175                | 350         | 995.8                 | 52.17                        | 377.85          | 309.15      | 0.4            |

## 2.3 Experimental Methods

### 2.3.1 Slump Test

The concrete mix has been designed as per IS 10262:2019. The workability test has been conducted for all the five mixes as per IS 1199:2008. The SP dosage used and the slump obtained for



each mix are presented in Table 6. A standard mould of 300mm height, 200mm base diameter and 100mm top diameter was used. The fresh concrete was filled into the mould in equal layers and well compacted. The subsidence was measured after the removal of the cone.

**Table 6: Slump Test Results**

| Sl No | Designation | SP % used | Slump(mm) |
|-------|-------------|-----------|-----------|
| 1     | EC0         | 0.45      | 60        |
| 2     | EC1         | 0.60      | 57        |
| 3     | EC2         | 0.67      | 58        |
| 4     | EC3         | 0.82      | 56        |
| 5     | EC4         | 1.05      | 57        |

### 2.3.2 Compressive Strength Test

A total of 18cubes of size 150×150×150mm (control, with 20 % ECA, with 20% ECA plus 0.1% PPF, with 20% ECA plus 0.2% PPF, with 20% ECA plus 0.3% PPF and with 20% ECA plus 0.4% PPF) were tested as per IS516: 1999 in a standard Compression Testing Machine. Each value represents the average result of three specimens in the same group.

A total of 18 cylinders of size 150×300 mm (control, with 20 % ECA, with 20% ECA plus 0.1% PPF, with 20% ECA plus 0.2% PPF, with 20% ECA plus 0.3% PPF and with 20% ECA plus 0.4% PPF) were tested as per IS 516: 1999 in a standard Compression Testing Machine. Each value represents the average result of three specimens in the same group.

### 2.3.3 Elasticity Modulus Test

A total of 18 cylinders of size 150×300 mm (control, with 20 % ECA, with 20% ECA plus 0.1% PPF, with 20% ECA plus 0.2% PPF, with 20% ECA plus 0.3% PPF and with 20% ECA plus 0.4% PPF) were tested as per IS 516: 1999 in a standard Compression Testing Machine. The test set-up with appropriate instrumentation for this experiment is shown in Figure 4. Each value represents the average result of three specimens in the same group.



**Figure 4: Elasticity Modulus Test on Cylinder**

### 2.3.4 Flexural Strength Test

A total of 18 prisms of size 100× 100 X 500 mm (control, with 20 % ECA, with 20% ECA plus 0.1% PPF, with 20% ECA plus 0.2% PPF, with 20% ECA plus 0.3% PPF and with 20% ECA plus 0.4% PPF) were tested as per IS 516: 1999 in a standard loading frame. Figure 5 shows the test. Each value represents the average result of three specimens in the same group.



**Figure 5: Flexure Test on Prism**


## 3 Results and Discussion

### 3.1 Compressive Strength


The compressive strength of expanded clay-based structural lightweight concrete with varying fibre volume fractions of polypropylene fibre is presented in Table 7. The average compressive strength of the expanded clay-based structural lightweight concrete specimens was 23.55 MPa which confirms ASTM 213R-03. There was an increase in compressive strength by 3.77 % and 10.40 % with the inclusion of 0.1% and 0.2% volume fraction of polypropylene fibres respectively. The compressive strength of concrete with 0.3% volume fraction of polypropylene fibres increased appreciably reaching a peak value of 28.22 N/mm<sup>2</sup>. The increase in cube strength may be due to the strong bond between the PP fibres and the matrix. However, the compressive strength of concrete with 0.4% volume fraction of polypropylene fibres got decreased. It is apparent that the decrease in compressive strength for this fibre content may be due to difficulty in dispersing the fibres in the concrete. The percentage gain in cube and cylinder compressive strength is shown in Figure 6 and Figure 7.

**Table 7: Compressive Strength Test Results**

| Designation | Cube Compressive Strength (MPa) | % Gain in Cube Compressive Strength | Cylinder Compressive Strength(MPa) | % Gain in Cylinder Compressive Strength |
|-------------|---------------------------------|-------------------------------------|------------------------------------|---|
| EC0         | 23.55                           | -                                   | 18.84                              | -                                       |
| EC1         | 24.44                           | 3.77                                | 19.58                              | 3.93                                    |
| EC2         | 26.00                           | 10.40                               | 20.94                              | 11.15                                   |
| EC3         | 28.22                           | 19.83                               | 22.64                              | 20.17                                   |
| EC4         | 25.42                           | 7.94                                | 20.37                              | 8.12                                    |

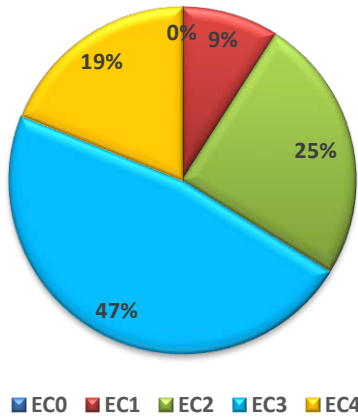

**Figure 6: Cube Compressive Strength**

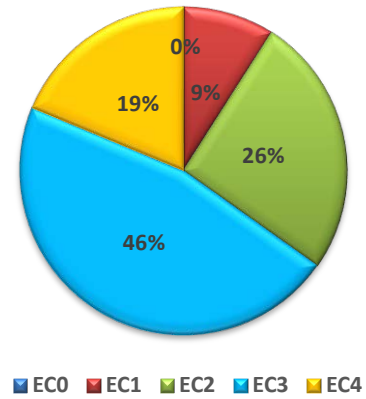

**Figure 7: Cylinder Compressive Strength**

### 3.1.1 Failure Pattern

The cube specimens were tested in a compression testing machine of 1000 kN capacity. The failure pattern of polypropylene fibre based lightweight concrete cube specimens with expanded clay aggregate is shown in Figure 8. In the early stages, the cracks were concentrated on the surface only. With the increase in axial stress level, the cracks formed earlier propagated towards the interior of the cube specimens. Further, Concrete spalling also occurred at this stage. With the inclusion of polypropylene fibres, the failure pattern of cube specimens changed distinctly. The propagation of crack was found retarded. This is because the internally included polypropylene fibres created a confinement mechanism preventing the tendency of concrete to crack and spall. The volume fraction of polypropylene fibres have been found to influence the failure pattern of cube specimens significantly.




**Figure 8: Failure Pattern of Cube specimens**

### 3.2 Modulus of Elasticity

The elasticity modulus of expanded clay-based structural lightweight concrete with varying fibre volume fractions of polypropylene fibre is presented in Table 8. The results exhibit an increase of 0.86% in fibre reinforced lightweight concrete when compared to non-fibre reinforced concrete. With the further addition of polypropylene fibres, the elasticity modulus increased. The addition of polypropylene fibres by 0.3% increases the elasticity modulus by 10.17%. Similarly, a 0.4% volume fraction of polypropylene fibre increases the elasticity modulus by 11.78%. The modulus of elasticity was found to increase with the increase in polypropylene fibre content due to the fibre bridging affecting the percentage gain in modulus of elasticity are shown in Figure 9.

**Table 8:** Elasticity Modulus Test Results

| Designation | Elasticity Modulus (GPa) | % Gain in Elasticity Modulus |
|-------------|--------------------------|------------------------------|
| EC0         | 24.39                    | -                            |
| EC1         | 24.60                    | 0.86                         |
| EC2         | 25.50                    | 4.55                         |
| EC3         | 26.87                    | 10.17                        |
| EC4         | 27.26                    | 11.78                        |

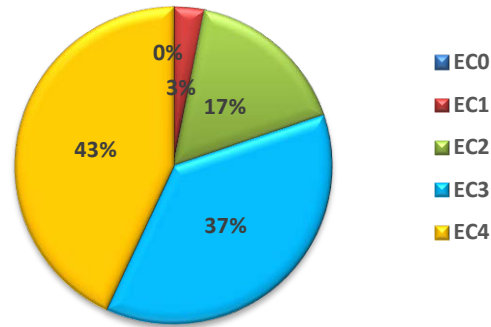

**Figure 9:** Modulus of Elasticity of Test Specimens

### 3.2.1 Failure Pattern

The cylinder specimens were tested in a compression testing machine of 1000 kN capacity. The failure pattern of polypropylene fibre based lightweight concrete cylinder specimens with expanded clay aggregate is shown in Figure 10. In the early stages, a major macro crack was observed over the height of the cylinder specimen. With an increase in axial compressive stress, more longitudinal cracks formed on the specimen surface. With the inclusion of polypropylene fibres, the failure pattern of cylinder specimens changed differently. The crack propagation was found retarded. There was also an increase in crack density. The polypropylene fibres caused a confinement mechanism preventing the tendency of concrete to crack and spall. The volume fraction of polypropylene fibres has been found to significantly influence the failure pattern of cylinder specimens.



**Figure 10:** Failure Pattern of Cylinder Specimens

### 3.3 Modulus of Rupture


The flexural strength test results of different mixes are presented in Table 9. Each test value is the mean value recorded from three test specimens. The flexural strength was found to increase from 4.7 N/mm<sup>2</sup> to 7.4 N/mm<sup>2</sup> with an increase in fibre volume fraction from 0% to 0.4%. The rate of increase of flexural strength was 10.64% to 54.45% based on the fibre volume fraction attempted. The increase in flexural strength with an increase in fibre volume fraction may be due to the fact



that, after matrix cracking, the polypropylene fibres continue to share the load. The fracture process consisted of progressive fibre debonding during which crack propagation occurred slowly. The final failure occurred due to unstable crack propagation when the fibres pulled out. Figure 11 illustrates the modulus of Rupture of expanded clay-based polypropylene fibre reinforced concrete.

**Table 9: Modulus of Rupture Test Results**


| Designation | Modulus of Rupture (MPa) | % Gain in Modulus of Rupture |
|-------------|--------------------------|------------------------------|
| EC0         | 4.7                      | -                            |
| EC1         | 5.2                      | 10.64                        |
| EC2         | 5.8                      | 23.40                        |
| EC3         | 6.5                      | 38.29                        |
| EC4         | 7.4                      | 57.45                        |

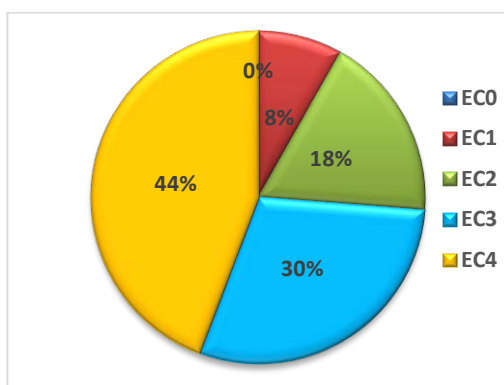

**Figure 11: Modulus of Rupture of Test Specimens**

### 3.3.1 Failure Pattern

The prism specimens were tested under four-point bending in a standard loading frame. The failure pattern of polypropylene fibre based lightweight concrete prism specimens with expanded clay aggregate is shown in Figure 12. The pattern of failure was found to be the same in the specimens with and without polypropylene fibres except that the time of formation of crack as well as the width of crack was less. The increase in flexural strength with an increase in fibre volume fraction may be due to the restraint to crack growth caused by the PP fibre addition.

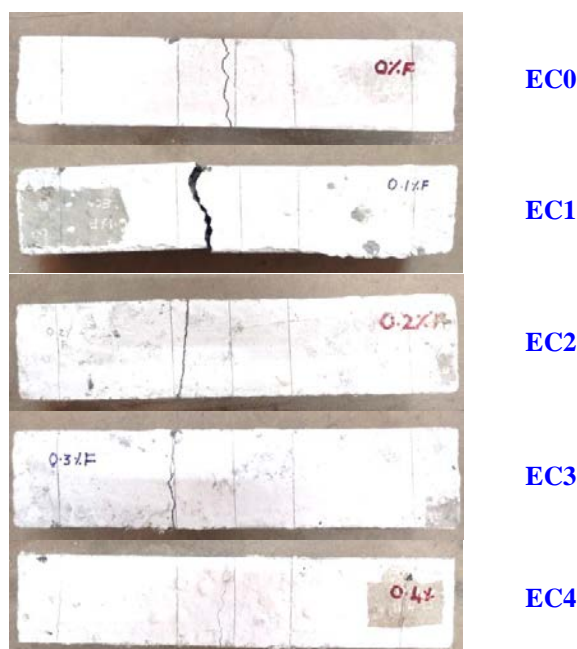

**Figure 17: Failure Pattern of Prism Specimens**

## 4 Conclusion

From this study, the expanded clay-based structural lightweight aggregate concrete showed a maximum of 19.83% increase in compressive strength with the inclusion of 0.3% volume fraction of polypropylene fibre., which may be due to the cracking resistance offered by the fibre reinforcement. The addition of polypropylene fibres is very effective in improving the flexural strength of structural lightweight concrete. A maximum increase of 57.45% has been obtained with 0.4% volume fraction of polypropylene fibres.

The modulus of elasticity increased at the rate of 0.86% to 11.78% as the fibre volume fraction increased from 0.1% to 0.4%. The incorporation of polypropylene fibres not only improves the overall performance of structural lightweight concrete but also helps in preventing the brittle failure of the material.

## 5 Availability of Data and Material

Data can be made available by contacting the corresponding author.

## 6 References

- Aghaee, K., Yazdi, M. A., & Tsavdaridis, K. D. (2015). Investigation into the mechanical properties of structural lightweight concrete reinforced with waste steel wires. *Magazine of Concrete research*, 67(4), 197-205.
- Bernardo, L. F., Nepomuceno, M. C., & Pinto, H. A. (2016). Flexural ductility of lightweight-aggregate concrete beams. *Journal of Civil Engineering and Management*, 22(5), 622-633.
- Chowdary, A., Chaithra, N, Chethan, K. (2017). A Study on Impact of Polypropylene (Recron 3S) Fibers on Compressive and Tensile Strength of Concrete. *International Journal for Innovative Research*, 4(3), 13-22.
- Gao, J., Sun, W., & Morino, K. (1997). Mechanical properties of steel fiber-reinforced, high-strength, lightweight concrete. *Cement and Concrete Composites*, 19(4), 307-313.
- Li, J., Niu, J., Wan, C., Liu, X., & Jin, Z. (2017). Comparison of flexural property between high performance polypropylene fiber reinforced lightweight aggregate concrete and steel fiber reinforced lightweight aggregate concrete. *Construction and Building Materials*, 157, 729-736.
- Lim, H. S., Wee, T. H., Mansur, M. A., & Kong, K. H. (2006, September). Flexural behavior of reinforced lightweight aggregate concrete beams. In *Proceedings of the 6th Asia-Pacific Structural Engineering and Construction Conference (APSEC 2006)* (pp. 5-6).
- Sakthivel, S.K., Saravanan, J. (2022). Experimental Assessment over Theoretical Prediction & Analytical Studies on Flexure Behavior of RC Beams with Recycled Coarse Aggregate. *International Transaction Journal of Engineering, Management, & Applied Sciences & Technologies*, 13(3), 13A3I, 1-11. <http://TuEngr.com/V13/13A3I.pdf> DOI: 10.14456/ITJEMAST.2022.51
- Sohaib, N., Seemab, F., Sana, G., & Mamoon, R. (2018). Using Polypropylene Fibers in Concrete to achieve maximum strength. In *Proc. of the Eighth International Conference on Advances in Civil and Structural Engineering* (pp. 36-42).



**K.K.Gaayathri** is a Research Scholar at the Department of Civil and Structural Engineering, Annamalai University, Annamalainagar, Tamil Nadu. She got her Master's Degree in Structural Engineering from Annamalai University, Annamalainagar-608001, Tamil Nadu. Her research is based on the Structural Light Weight Concrete with various percentages of Micro Reinforcements.



**Dr.K.Suguna** is a Professor at the Department of Civil and Structural Engineering, Annamalai University, Annamalainagar-608001, Tamil Nadu. She got her Master's and PhD degrees in Structural Engineering, Annamalai University, Annamalainagar-608001, Tamil Nadu. Her research focuses on FRP laminates and fibre reinforced concrete.



**Dr.P.N.Raghunath** is a Professor at the Department of Civil and Structural Engineering, Annamalai University, Annamalainagar-608001, Tamil Nadu. He got his Master's and PhD degrees in Structural Engineering, Annamalai University, Annamalainagar-608001, Tamil Nadu. His research focuses on FRP Laminates and Fibre Reinforced Concrete.

---